Synthesis and Stability of NaSICON for Sodium-Based Batteries

Dr. Erik D. Spoerke, Dr. Nelson Bell, Dr. Frank Delnick, Cynthia Edney, Bonnie McKenzie

*Team Lead: Dr. David Ingersoll - Sandia National Laboratories, Albuquerque, NM USA

Drs. D. Ingersoll, E. Spoerke, N. Bell, F. Delnick, T. Anderson, R. Cygan, K. Zavadil, C. Apblett, J. Ihlefeld; Sandia National Laboratories – ion transport, long term stability, cathode chemistry, and prototype development

Prof. E. Wachsman; University of Maryland – solid-state ionics

Dr. S. Bhavaraj, Ceramatec – prototype development and ceramic supplier

Profs. R. Kee, J. Porter, Colorado School of Mines – system-level modeling and simulation (Mod-Sim), advanced spectroscopy.

Why NaSICON?

(Sodium (**Na**) **S**uper **I**onic **Con**ductor)

$$Na_{1+x}Zr_2P_{3-x}Si_xO_{12} \xrightarrow{x = 2} Na_3Zr_2PSi_2O_{12}$$

NaSICON is a high conductivity (up to 10^{-2} S/cm at room T°C) solid state electrolyte that is stable against molten sodium and which we are using in development of a family of sodium-based battery technologies.

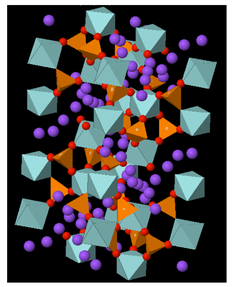

Select batteries under development

1. Sodium-air
2. Sodium-ion
3. Low temperature sodium-sulfur
4. Sodium-bromine: $Na + \frac{1}{2} Br_2 \leftrightarrows Na^+ + Br^-$ 3.79 V 987 Wh/kg
5. Sodium-iodine: $Na + \frac{1}{2} I_2 \leftrightarrows Na^+ + I^-$ 3.25 V 581 Wh/kg

Programmatic Goals and Objectives

- Reduce the cost of energy to < 100 $/kWh
- Develop a suite of sodium-based battery solutions to fill the multiple application needs for stationary storage
- Facilitate short development timeframe

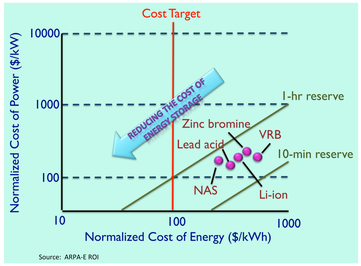

Fully realizing sodium battery potential will require stable, high conductivity NaSICON.

The Chemistry of NaSICON – Toward understanding and optimizing behavior

- NaSICON is a multi-component material having complex chemistry.
- High temperature synthetic routes often produce secondary "contaminant" phases.
- These secondary phases can and do dramatically affect *performance and stability.*

Our approach:

1) study the effects that secondary phases have on performance
2) determine how to tailor the phase composition in order to control performance
3) prepare improved materials based on this increased understanding of NaSICON's complex chemistry

ZrO_2 Phase Leads to Reduced Conductivity

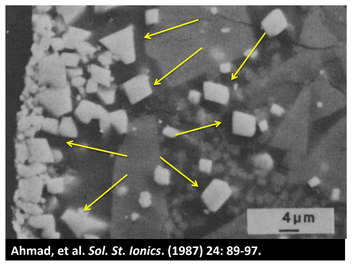

Scanning electron micrograph of monoclinic ZrO_2 in NaSICON produced at 1300°C sintering temperature.

Ionic conductivity decreases with excess ZrO_2.

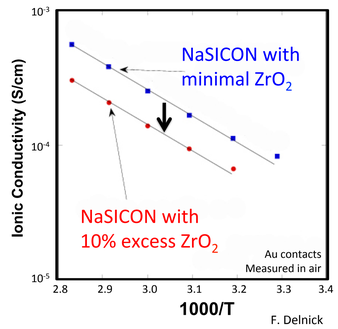

Decreased ionic conductivity leads to decreased battery performance. How can we address excess ZrO_2?

Engineered sol-gel processing allows for lower temperature processing and tailoring of NaSICON composition to address secondary ZrO_2 formation.

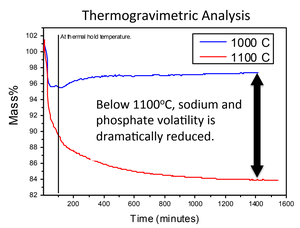

Reducing firing temperature below 1100°C or introducing a small excess of sodium to the sol-gel precursors dramatically reduces ZrO_2 formation.

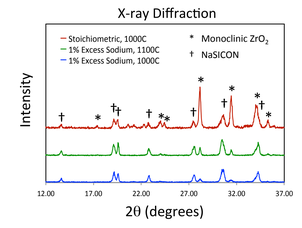

Glassy Phases Reduce Stability

Glassy silicate and phosphate phases reduce NaSICON stability, thereby compromising reliability.

Glassy phases, particularly sodium phosphates, decrease stability in alkaline electrolytes.

Silicate Glasses

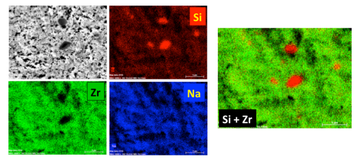

Phosphate Glasses

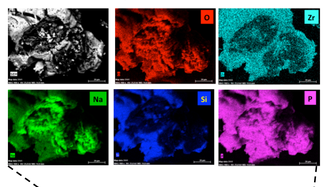

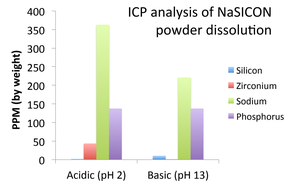

Aqueous powder dissolution studies (7 days, RT):

- Zr-solubility in acid
- Si-solubility in base
- Na, PO_4 solubility under all conditions



Under alkaline conditions (14 days, RT) NaSICON pellets show signs of physical degradation.

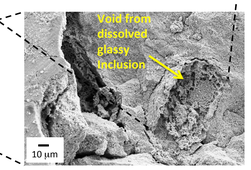

Dissolution of phosphate glassy particles is implicated in the degradation of NaSICON.

Refinement of NaSICON conversion chemistry and sintering conditions are expected to address deleterious glass formation.

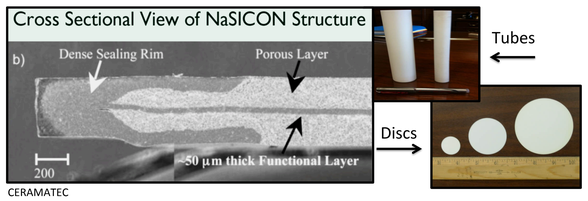

CERAMATEC

Enabling Prototype Development

Optimized NaSICON conductivity and stability will enable advanced ceramic structures for versatile, efficient battery development.

- No crossover, eliminates cathode-anode materials compatibility issues
- Planar bipolar stacks & flow designs are possible

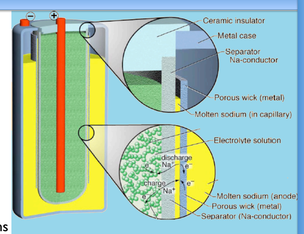

R. Kee, conceptual designs

The authors gratefully acknowledge the support of Dr. Imre Gyuk and the Department of Energy/Office of Electricity's Energy Storage Program.

Sandia National Laboratories is a multi-program laboratory managed and operated by Sandia Corporation, a wholly owned subsidiary of Lockheed Martin Corporation, for the U.S. Department of Energy's National Nuclear Security Administration under contract DE-AC04-94AL85000.